

Superconductivity, magnetic ordering, and its interplay in $\text{HoNi}_2^{11}\text{B}_2\text{C}$

A. Dertinger^{a,1}, A. Kreyssig^b, C. Ritter^c, M. Loewenhaupt^b, and H.F. Braun^a

^a*Physikalisches Institut, Experimentalphysik V, Universität Bayreuth, D-95440 Bayreuth, Germany*

^b*Institut für Angewandte Physik, Technische Universität Dresden, D-01062 Dresden, Germany*

^c*Institut Max von Laue - Paul Langevin, 156 X, F-38042 Grenoble, France*

Abstract

We investigated the low-temperature properties of polycrystalline $\text{HoNi}_2^{11}\text{B}_2\text{C}$ by means of ac-susceptibility and neutron powder diffraction in the temperature range of 1.5 to 10 K and zero magnetic field. A sample with pronounced re-entrant behaviour was chosen since it exhibits a superconducting state which is strongly affected by the intrinsic magnetism, the formation of long range magnetic order, via pair-breaking. The evolution and volume fractions of the three different magnetic structures were observed and correlated to the superconducting behaviour.

Keywords: superconductivity; magnetic order; borocarbides

1. Introduction

In the family of the quaternary borocarbides $R\text{Ni}_2\text{B}_2\text{C}$, co-existence of superconductivity and antiferromagnetism of the rare earth ions has been found at low temperatures for $R = \text{Tm}, \text{Er}, \text{Ho}$, and Dy (see e.g. [1,2]). In the case of $\text{HoNi}_2\text{B}_2\text{C}$, the transition temperatures for both ordering phenomena lie in the same temperature region of about 5 to 8 K. Hence, this system offers an ideal possibility to study the interplay between magnetism and superconductivity. Three different magnetic structures have been identified for $\text{HoNi}_2\text{B}_2\text{C}$: a commensurate antiferromagnetic one with wave vector $\tau_1 = (0, 0, 1)$, an incommensurate structure with $\tau_2 = (0, 0, 0.915)$ and an incommensurate structure with

$\tau_3 = (0.585, 0, 0)$ [1,3]. While for flux-grown single crystals only an ordinary superconducting transition has been observed in zero magnetic field, the low-temperature properties of polycrystalline samples strongly depend on thermal treatment [4] as well as on their chemical composition within a small but non-negligible homogeneity range [5]. Pure superconductivity co-existing with antiferromagnetism, re-entrant behaviour, as well as samples in a non-superconducting but magnetically ordered state down to at least 1.5 K have been found [6]. The study of different polycrystalline samples can therefore reveal correlations between the complicated set of magnetic structures and the occurrence of superconductivity. In this paper, we will present results on a sample with pronounced re-entrant behaviour in zero magnetic field.

¹ Corresponding author: armin.dertinger@uni-bayreuth.de

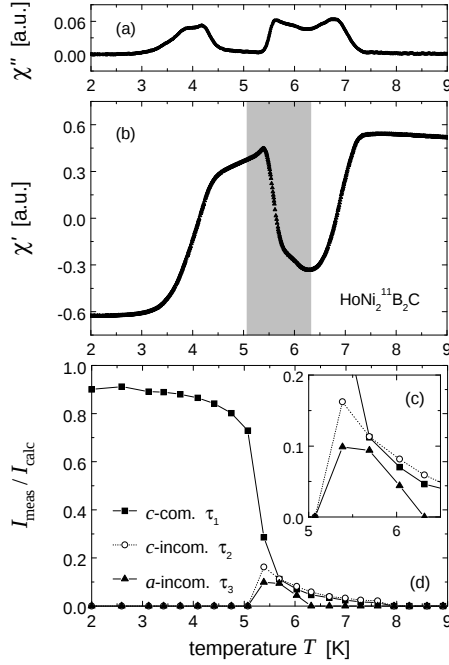


Fig. 1. Temperature dependence of the real and imaginary part of the ac-susceptibility χ' (b) and χ'' (a) and of the intensities of the magnetic reflections τ_1 , τ_2 and τ_3 (d), corresponding to the commensurate c -axis, the incommensurate c -axis and the incommensurate a -axis modulated structure, respectively. The inset (c) shows an enlargement of the intensities of τ_2 and τ_3 . All intensities are normalized by the calculated intensity for the fully magnetically ordered phase with the free ion value of $10 \mu_B$ for Ho^{3+} . The shaded area in (b) corresponds to the temperature interval where the a -incommensurate structure exists.

2. Experimental

The $\text{HoNi}_2^{11}\text{B}_2\text{C}$ sample was prepared by arc-melting stoichiometric amounts of the pure elements on a water-cooled copper hearth under argon atmosphere. 10 at.-% excess carbon were added to compensate for evaporation losses. The sample was remelted several times and then annealed for 16 days at 1100°C to ensure its homogeneity. Phase purity was checked by X-ray powder diffraction. Only minor traces of HoB_2C_2 could be detected. The ac-susceptibility measurements were performed at 22 Hz with an ac-amplitude of 0.1 mT. The neutron powder diffraction experiment was carried out at the multidetector instrument D1B at the ILL in Grenoble.

3. Results and discussion

The ac-susceptibility measurements can be seen in Fig. 1 b. The sample becomes superconducting at 7.1 K, re-enters the normal state below roughly 6.3 K, and finally becomes superconducting again at about 4.3 K. Each transition between superconducting and normal state, and vice versa, is accompanied by a loss signal in the quadrature part of the susceptibility χ'' (Fig. 1 a).

The neutron scattering data in Fig. 1 d show first signs of long range magnetic ordering with the appearance of the two c -axis modulated structures at about 8 K. Their tail exists well above the superconducting transition temperature whereas the a -axis modulated structure is confined to a very small temperature interval below T_c (see Fig. 1 c). This temperature region is highlighted by shading in the susceptibility plot and is exactly where the sample re-enters the normal state. It indicates that this structure is responsible for the observed pair-breaking which leads to re-entrant behaviour. This interpretation is in very good agreement with neutron scattering experiments on samples with non-magnetic dilutions on the Ho-site [3,7]. However, the normal state persists below the temperature where the a -incommensurate structure vanishes. Below 5 K, only the c -commensurate groundstate is observed and superconductivity returns at 4.3 K.

We gratefully acknowledge the assistance of W. Ettig and A. Krause. This work was partially supported by the DFG through SFB 463.

References

- [1] J.W. Lynn *et al.*, Phys. Rev. B 55, 6584 (1997).
- [2] P.C. Canfield *et al.*, Phys. Today 51, 40 (1998).
- [3] A. Kreyssig *et al.*, Physica B 234-236, 737 (1997).
- [4] H. Schmidt *et al.*, J. Alloys & Compounds 262-263, 459 (1997); T.A. Wagner *et al.*, Physica C (1999).
- [5] H. Schmidt and H.F. Braun, in: Studies of High Temp. Supercond. 26, Nova Science Publishers, NY, 47 (1998).
- [6] H. Schmidt *et al.*, Physica C 256, 393 (1996).
- [7] A. Kreyssig *et al.*, Physica B 241-243, 826 (1998).